

INVESTIGATION OF THE PROPERTIES OF CONCRETE BASED ON NON-FIRING ALKALINE BINDERS

Khamidov Adhamjon

Professor of Namangan Engineering-Construction Institute

Akhmedov Islombek

Dasent of Namangan Engineering-Construction Institute

Kholmirezayev Sattor

Professor of Namangan Engineering-Construction Institute

Qodirova Feruza

Teacher of Namangan Engineering-Construction Institute

Nomonova Sohiba

Teacher of Namangan Engineering-Construction Institute

Sharopov Begyor

Teacher of Namangan Engineering-Construction Institute

Kazadayev Aleksandir

Teacher of Namangan Engineering-Construction Institute

<https://doi.org/10.5281/zenodo.7448002>

Abstract. *The article deals with the use of film-forming materials for the care of freshly laid concrete based on non-firing alkaline binders, the results of studies to determine the strength, frost resistance and plastic shrinkage of concrete are presented.*

Keywords: *Concrete, unfired alkaline binder, fresh concrete care, film-forming materials, strength, frost resistance, plastic shrinkage.*

ИССЛЕДОВАНИЕ СВОЙСТВ БЕТОНОВ НА ОСНОВЕ НЕГОРЮЧИХ ЩЕЛОЧНЫХ ВЯЖУЩИХ

Аннотация. *В статье рассмотрено применение пленкообразующих материалов для ухода за свежесуложенным бетоном на основе негорючих щелочных вяжущих, представлены результаты исследований по определению прочности, морозостойкости и пластической усадки бетона.*

Ключевые слова: *Бетон, необожженное щелочное вяжущее, уход за свежим бетоном, пленкообразующие материалы, прочность, морозостойкость, пластическая усадка.*

INTRODUCTION

One of the main priority areas of market economic reforms is the expansion of production of high quality export-oriented and import-substituting products. Among these top-priority industries is the building materials industry, which has a strong potential and great importance for the development of the construction complex. It is known that the most priority direction in the building materials industry is the production of mineral binders and various materials based on them.

In the world practice of construction, the demand for cement concrete is increasing as an alternative and effective structural material. According to the International Federation for Structural Concrete (FIB), at present, the annual production of cement in the world is approximately 4 billion tons, and the production of concrete based on it on a global scale is

approaching 12.0 billion m³ in year. The first decade of the 21st century was marked by significant advances in the development of new cement concrete technologies.

Portland cement is one of the most popular and at the same time scarce technical products of our time, which has many wonderful properties that have made it the bread of construction.

However, Portland cement, along with undeniable advantages, also has serious disadvantages. These are, first of all, high energy consumption (clinker firing temperature 14500C), relatively low activity (40 ... 60 MPa), lack of interaction with clay and dust particles, the need to use large and small aggregates.

And in this regard, the production of unburned alkaline binders (BSC) from industrial waste is of great interest, the production technology of which is simple and environmentally friendly.

RESEARCH MATERIALS AND METHODOLOGY

For the manufacture of unburned alkaline binders in Uzbekistan, there are sufficient raw materials in the form of many tonnage waste from the metallurgical, chemical and energy industries.

The main raw materials for the production of non-firing alkaline binders are aluminosilicate slags (electrothermophosphoric, electric steel-smelting), burnt rock (gliezhi), rock (tuffite), active mineral additive (Portland cement or cement clinker), alkaline component (soda sulfate mixture, baking dust, etc.) . It should be noted that in the preparation of concretes based on unfired alkaline binders, it is possible to use fine aggregates containing a large amount of dust and clay particles, while, in concretes based on Portland cement, the presence of these particles is limited by standards.

The main technology for the production of non-calcined alkaline binders is the drying of raw materials, dosage and grinding.

Non-firing alkaline binders have a number of physical-mechanical and technical-operational characteristics that significantly exceed those of many other mineral binders and composites based on them. Low costs of heat and electricity for their production, a wide range of compressive strength of binders (from 20 to 180 MPa) and concrete (from 0.5 to 150 MPa) substantiate their versatility. The highly active non-firing alkaline binder, which is part of the concrete, makes it possible, due to the increased adhesion to aggregates, to obtain a material with a compressive strength of 49-50 MPa. It should also be noted that this type of binder is environmentally friendly, which is very important in conditions of environmental pollution (especially in the production of Portland cement). In this regard, extensive scientific research is being conducted in Uzbekistan to expand the use of these binders in construction.

It is known that the durability of concrete and reinforced concrete structures and structures depends not only on the composition of concrete and the quality of materials used for its preparation, but also on the conditions for the formation of its structure and basic properties (temperature and humidity of the environment at which laying and subsequent curing takes place) .

In Uzbekistan, characterized by a dry and hot climate, the relative air humidity during the day in summer at a temperature of more than 450C is 10%. The surface temperature of freshly laid concrete on sunny days reaches 60-700C. As a result, intensive evaporation of mixing water occurs, the processes of structure formation are accelerated, concrete mixtures quickly lose their plastic properties. Intensive evaporation of mixing water from freshly laid concrete can

significantly slow down or even completely stop the process of increasing its strength. In addition, the evaporation of moisture from the freshly laid concrete mix has a negative effect on the formation of the concrete structure, a network of through microchannels is formed in it, reducing its strength, deformation and operational characteristics.

RESULTS OF THE STUDY

The filtration capacity of freshly laid concrete curing in dry and hot climates is 70% greater than that of concrete curing in "normal" conditions. This indicator also negatively affects the strength and performance capabilities of concrete. In this regard, it is necessary to take care of freshly laid concrete in order to protect it from moisture loss.

In practice, when laying concrete mixtures, various methods of care are used. As you know, one of the effective ways of care is the use of film-forming materials. There are a number of works devoted to the use of film-forming materials for cement concrete [4,5]. However, the issues of using film-forming materials for the care of concrete mixtures based on non-firing alkaline binders have been little studied.

At the Namangan Civil Engineering Institute, at the department "Production of building materials, products and structures", research was carried out on the selection of film-forming materials that form a strong film in an alkaline environment. More than 30 different film-forming compositions have been studied to meet the goals.

According to the research results, the most effective film-forming composition that meets the technical requirements and forms a waterproof film in an alkaline environment and well protects concrete from moisture loss in dry and hot climates was a water-based film-forming material (water-soluble composition-WRC).

In the future, to study the issue of using film-forming materials for the care of freshly laid concrete based on non-firing alkaline binders, studies were carried out using WRC.

Characteristics of the materials used to prepare 1 m³ of concrete:

The composition of the concrete mix (1:2.21:4.62, W/C=0.56).

Type of binder - non-firing alkaline binder grade 400 - 333 kg.

Large aggregate - crushed granite (fr. 5-20 mm.) - 1539 kg.

Fine aggregate - quartz sand M_{cr} = 1.64 - 736 kg.

Water - 187 l

The film-forming material is a water-soluble composition (WRC).

The design strength of concrete (standard) is 40 MPa.

The materials used comply with the requirements of GOST.

To determine the compressive strength of concrete during solar thermal treatment, samples with dimensions of 150x150x150 mm were prepared.

Forms filled with a concrete mixture based on non-firing alkaline binders were compacted on a vibrating table, and film-forming materials were immediately applied to the surface of the samples with a paint sprayer. The consumption of film-forming materials in this case amounted to 200-250 g/m². After applying the film-forming materials, one series of samples was placed in a climatic chamber at t = 40°C and humidity W = 30% for keeping, the other series was placed in a chamber of normal conditions (t = 20°C + 20°C, W = 95-98%). The samples were tested after 1, 2, 3, 7, 28 and 90 days of storage in the chambers. The test results are shown in table-1

Table 1.

Strength of concrete during solar treatment

| Hardening conditions | Compressive strength of concrete, day | | | | |
|--------------------------------|---------------------------------------|---------------------|---------------------|----------------------|----------------------|
| | 1 | 3 | 7 | 28 | 90 |
| Normal conditions | - | - | - | <u>39,8</u> 100 | - |
| climate chamber (using VRK) | <u>15,4</u> 39,49 | <u>25,0</u> 64,1 | <u>37,0</u> 94,9 | <u>41,7</u> 106,9 | <u>43,0</u> 110,3 |
| no care | - | - | - | <u>21,0</u> 53,8 | - |

Note: Above the line, the strength of concrete in MPa, below the line in % (compared to the strength of samples hardened for 28 days under normal conditions).

As can be seen from the table, the strength of concrete samples hardened under the film-forming composition was 15.4 MPa or 39.49% after 1 day of hardening, 25 MPa or 64.1% after 3 days, 37.0 MPa or 94.9% after 7 days. % (compared to the strength of samples hardened for 28 days under normal conditions). An intensive increase in the strength of concrete is a consequence of helio-heat treatment with the prevention of moisture evaporation. Despite the intensive increase in the strength of unfired alkaline binders in the early stages of hardening, their heat release is low (1.5-2.5 times less than that of Portland cement).

The results obtained show an increase in the strength of concrete (based on non-firing alkaline binders), hardened under the film-forming composition due to the complete hydration processes.

To determine the frost resistance of concrete based on unfired alkaline binders, samples of the same composition of the concrete mixture were prepared as indicated above and based on the requirements of GOST 10060. "Concrete. Determination of frost resistance. tests have been carried out.

According to GOST, the concrete grade for frost resistance: an indicator of frost resistance of concrete corresponding to the number of freezing and thawing cycles of samples determined during testing by basic methods, in which the concrete characteristics established by the standard remain within normalized limits and there are no external signs of destruction (cracks, chips, peeling of sample edges). The test results are shown in table 2.

Table 2.

Frost resistance and strength of concrete during solar treatment

| Hardening conditions | Compressive strength of concrete, MPa | | | | Frost resistance, cycle |
|----------------------|---------------------------------------|-------------------------|-----------------------|-------------------------|-------------------------|
| | Before test 100 cycle | After testing 100 cycle | Before test 150 cycle | After testing 150 cycle | |
| Normal conditions | 40,5 | 38,0 | 41,0 | 39,0 | 150 |

| | | | | | |
|--|------|------|------|------|-----|
| Solar thermal treatment (using VRK) | 40,7 | 36,8 | 41,7 | 39,1 | 150 |
| no care | 28,7 | 21,0 | - | - | 75 |

As can be seen from Table 2, during solar thermal treatment using a film-forming composition, the frost resistance of the samples was 150 cycles. This indicator is close to the indicators of concrete samples hardening under normal conditions. For samples hardened without maintenance, frost resistance was only 75 cycles.

One of the most important problems of concreting in a dry hot climate is the all-round limitation and elimination of various physical destructive processes occurring in concrete in the initial period of hardening. A special place among them is occupied by plastic shrinkage, which is one of the main causes of early cracking of concrete.

To measure the plastic shrinkage of freshly molded concrete, a device proposed by E.N. Malinsky was used.

An indirect assessment of film-forming materials from the point of view of the occurrence of plastic shrinkage is proposed to be carried out using the coefficient of caring for a long loaf K_{ef} , determined by the formulas:

$$K_{ef} = 1 - \frac{E_i - E_0}{E_{max} - E_0} \quad \text{or} \quad K_{ef} = \frac{E_{max} - E_i}{E_{max} - E_0}$$

Where E_0 - initial deformations of freshly laid concrete with the exclusion of evaporation, mm/m;

E_{max} - maximum value of plastic shrinkage of concrete hardening without maintenance, mm/m;

E_i - the value of plastic shrinkage of concrete protected from dehydration by the studied film-forming material, mm/m.

As follows from the above formulas, the film-forming material will have the highest concrete ($K_{ef} = 1$) care efficiency, when applying which $E_i = E_0$, and the worst - when $E_i = E_{max}$ ($K_{ef} = 0$).

To determine the plastic shrinkage of freshly laid concrete based on unfired alkaline binders, hardened under a film-forming coating, samples of the same composition of the concrete mix were prepared as indicated above.

Plastic shrinkage of heavy concrete of the above composition and moisture loss in% of mixing water are shown in figure-1

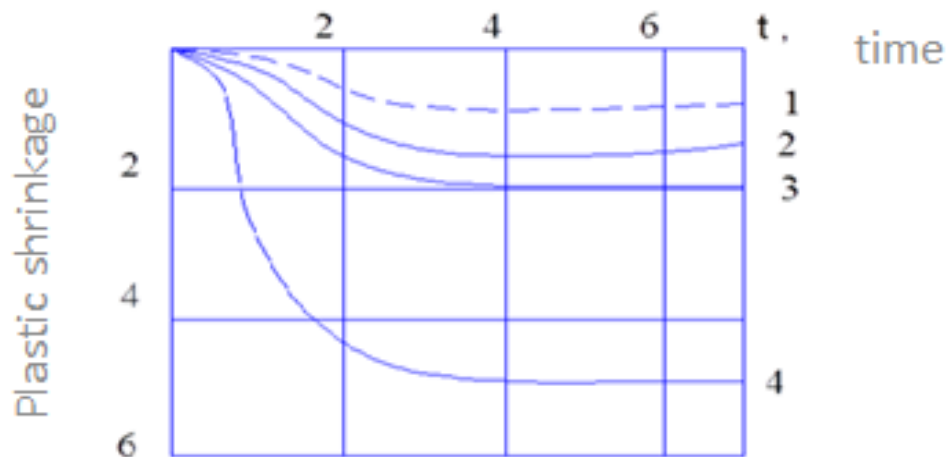


figure-1. The dependence of plastic shrinkage on the type of care

- 1.covering concrete with a layer of moistened sand
- 2.sample aged under VRK;
- 3.sample aged under polyethylene film (h=200mcr)
4. Uncoated sample

It can be seen from the given data that the K_{ef}^2 values of the concrete care when using the water-soluble composition and the K_{ef}^3 v -polyethylene film were 0.90 and 0.81, respectively.

As can be seen from Figure 1, the plastic shrinkage of concrete hardened under a water-soluble film-forming composition is insignificant and close to that of concrete hardening under a layer of moistened sand.

CONCLUSIONS

Based on the results of the studies, it can be concluded that when applied to a freshly laid concrete surface, film-forming compositions and heliothermal treatment (comparable to dry and hot climate conditions), moisture loss is prevented and the "soft" hardening mode provides high strength and frost resistance, as well as from the standpoint reduction of plastic shrinkage, the use of the studied composition for the care of freshly laid concrete based on unfired alkaline binders is very effective.

REFERENCES

1. Fathulloev A.M., Eshev S.S., Samiev L.N., Ahmedov I.G'., Jumaboyev X., Arifjanov S. Boglanmagan gruntlardan tashkil topgan uzanlarda yuvilmaslik tezliklarini aniklash [To the determination of non-effective speed in the beds containing from unconnected soils] //Journal "Irrigatsiya va melioratsiya". Tashkent. – 2019. – C. 27-32.
2. Arifjanov A., Akmalov Sh., Akhmedov I., Atakulov D. Evaluation of deformation procedure in waterbed of rivers //IOP Conference Series: Earth and Environmental Science. – IOP Publishing, 2019. – T. 403. – №. 1. – C. 012155.
3. Arifjanov A., Samiyev L., Akhmedov I., Atakulov D. Innovative Technologies In The Assessment Of Accumulation And Erosion Processes In The Channels //Turkish Journal of Computer and Mathematics Education (TURCOMAT). – 2021. – T. 12. – №. 4. – Pp. 110-114.

4. Axmedov I.G', Muxitdinov M., Umarov I., Ibragimova Z. Assessment of the effect of sedibles from sokhsoy river to kokand hydroelectric power station //InterConf. – 2020.
5. Arifjanov A.M., Ibragimova Z.I., Axmedov I.G'. Analysis Of Natural Field Research In The Assessment Of Processes In The Foothills The American Journal of Applied sciences. – 2020. – Т. 2. – №. 09. – Pp. 293-298.
6. Арифжанов А.М., Самиев, Л.Н., Абдураимова, Д.А., Ахмедов, И.Г. Ирригационное значение речных наносов [Irrigation value of river sediments] //Актуальные проблемы гуманитарных и естественных наук. – 2013. – №. 6.
7. Ахмедов И.Ф., Ортиқов И.А., Умаров И.И. Дарё ўзанидаги деформацион жараёнлаарни баҳолашда инновацион технологиялар [Innovative technologies in the assessment of deformation processes in the riverbed] // Фарғона политехника институти илмий-техника журнали. – Фарғона. – 2021. – Т.25, №.1. – С. 139-142.
8. Axmedov I.G', Ortiqov I.A., Umarov I.I. Effects of water flow on the erosion processes in the channel of GIS technology // <https://doi.org/10.5281/zenodo.5819579>
9. Tadjiboyev S., Qurbonov X., Akhmedov I., Voxidova U., Babajanov F., Tursunova E., Xodjakulova D. Selection of Electric Motors Power for Lifting a Flat Survey in Hydraulic Structures // AIP Conference Proceedings 2432, 030114 (2022); <https://doi.org/10.1063/5.0089643>
10. Abduraimova D., Rakhmonov R., Akhmedov I., Xoshimov S., Eshmatova B. Efficiency of use of resource-saving technology in reducing irrigation erosion // AIP Conference Proceedings 2432, 040001 (2022); <https://doi.org/10.1063/5.0089645>
11. Холмирзаев С. А., Комилова Н. Х. Влияние сухого жаркого климата на ширину раскрытия трещин внецентренно-сжатых железобетонных элементов //Приволжский научный вестник. – 2015. – №. 4-1 (44).
12. Холмирзаев С. А. Температурные изменения в керамзитобетонных колоннах в условиях сухого жаркого климата //Журнал «Бетон и железобетон. – 2001. – №. 2.
13. СА Холмирзаев, АР Ахмедов. Базальт толасининг тўлдирувчи сифатида цемент тошининг мустаҳкамлик хоссаларига таъсирини ўрганиш
14. Ijtimoiy fanlarda innovasiya onlayn ilmiy jurnali 2 (6), 49-55 2022
15. Хамидов А. И. и др. Использование теплоизоляционного композиционного гипса в энергоэффективном строительстве. – 2021.
16. Хамидов А. И., Нуманова С. Э., Жураев Д. П. У. Прочность бетона на основе безобжиговых щелочных вяжущих, твердеющего в условиях сухого и жаркого климата //Символ науки. – 2016. – №. 1-2. – С. 107-109.
17. Нуманова С. Э. Хамидов Адхамжон Иномжонович //ISSN 2410-700X. – С. 107.
18. Хамидов А. И., Ахмедов И., Кузибаев Ш. Теплоизоляционные материалы на основе гипса и отходов сельского хозяйства. – 2020.
19. Хамидов А. И. Использование теплоизоляционных материалов для крыш в энергоэффективном строительстве //Научно–технический журнал ФерПИ. Спец. – №. 2018.
20. Хамидов А. И., Мухитдинов М. Б., Юсупов Ш. Р. Физико-механические свойства бетона на основе безобжиговых щелочных вяжущих, твердеющих в условиях сухого и жаркого климата. – 2020.

21. Нуриддинов А. О., Ахмедов И., Хамидов А. И. АВТОМОБИЛ ЙЎЛЛАРИНИ ҚУРИЛИШИДА ИННОВАЦИЯЛАР //Academic research in educational sciences. – 2022. – Т. 3. – №. TSTU Conference 1. – С. 73-77.
22. Нуманова С. Э. Хамидов Адхамжон Иномжонович //ISSN 2410-700X. – С. 107.
23. Ризаев Б. Ш. Прочность, деформативность и трещиностойкость внецентренно-сжатых железобетонных элементов в условиях сухого жаркого климата. – 1993.
24. Абдуназаров, А., Хакимов, С., Умаров, И., Мухторалиева, М., Дедаханов, Ф., & Шаропов, Б. (2022). МЕРОПРИЯТИЯ ПО ПОВЫШЕНИЮ ЭНЕРГОЭФФЕКТИВНОСТИ СОВРЕМЕННЫХ И РЕКОНСТРУИРУЕМЫХ ЗДАНИЙ. Journal of new century innovations, 18(1), 130-134.
25. Hakimov, S., Sharopov, B., Umarov, I., Muxtoraliyeva, M., Dadaxanov, F., & Abdunazarov, A. (2022). URILISH MATERIALLARI SANOATIDA INNOVATSION MATERIALLAR ISHLAB CHIQRISHNING ISTIQBOLLI TOMONLARI. Journal of new century innovations, 18(1), 149-156.
26. Sharopov, B., Hakimov, S., Umarov, I., Muxtoraliyeva, M., Dadaxanov, F., & Abdunazarov, A. (2022). QUYOSH ENERGIYASIDAN FOYDALANIB TURAR JOY BINOLARI QURISHNING ISTIQBOLI TOMONLARI. Journal of new century innovations, 18(1), 135-141.
27. Sodiqjon, K., Begyor, S., Aleksandr, K., Farrukh, D., Mukhtasar, M., & Akbarjon, A. (2022). PROSPECTIVE ASPECTS OF USING SOLAR ENERGY. Journal of new century innovations, 18(1), 142-148.
28. Kazadayev, A., Sharopov, B., Hakimov, S., Umarov, I., Muxtoraliyeva, M., Dadaxanov, F., & Abdunazarov, A. (2022). MAMLAKATIMIZDA NEMIS TA'LIM TIZIMINI JORIY QILISHNING SAMARADORLIGI TAHLILI. Journal of new century innovations, 18(1), 124-129.
29. Mukhtasar, M., Begyor, S., Aleksandr, K., Farrukh, D., Isroil, U., Sodiqjon, K., & Akbarjon, A. (2022). ANALYSIS OF THE EFFECTIVENESS OF THE DEVELOPMENT OF THE GERMAN EDUCATION SYSTEM IN OUR COUNTRY. Journal of new century innovations, 18(1), 168-173.
30. Dadaxanov, F., Sharopov, B., Umarov, I., Mukhtoraliev, M., Hakimov, S., Abdunazarov, A., & Kazadayev, A. (2022). PROSPECTS OF INNOVATIVE MATERIALS PRODUCTION IN THE BUILDING MATERIALS INDUSTRY. Journal of new century innovations, 18(1), 162-167.
31. Begyor, S., Isroil, U., Aleksandr, K., Farrukh, D., Mukhtasar, M., Sodiqjon, K., & Akbarjon, A. (2022). MEASURES TO IMPROVE THE ENERGY EFFICIENCY OF MODERN AND RECONSTRUCTED BUILDINGS. Journal of new century innovations, 18(1), 157-161.
32. Kodirova F. M., Negmatov U. Algorithms For Stable Estimation Of The Extended State Vector Of Controlled Objects //Solid State Technology. – 2020. – Т. 63. – №. 6. – С. 14903-14909.
33. Кодиров Д. Т., Кодирова Ф. М. Алгоритмы совместного оценивания вектора состояния и параметров динамических систем //Universum: технические науки. – 2021. – №. 7-1 (88). – С. 66-68.
34. Кодиров Д. Т., Кодирова Ф. М. Перспективные энергоносители будущего //Вестник Науки и Творчества. – 2020. – №. 5 (53). – С. 50-53.

35. Кодирова Ф. М. Получение кондиционных углеводов переработкой пироконденсата и подземной газификацией угля компаундированием //Вестник Науки и Творчества. – 2017. – №. 7 (19). – С. 15-18.
36. Yuvmitov A., Hakimov S. R. Influence of seismic isolation on the stress-strain state of buildings //Acta of Turin Polytechnic University in Tashkent. – 2021. – Т. 11. – №. 1. – С. 71-79.
37. Ювмитов А., Хакимов С. Исследование влияния сейсмоизоляции на динамические характеристики ЗДАНИЯ //Acta of Turin Polytechnic University in Tashkent. – 2020. – Т. 10. – №. 2. – С. 14.
38. Abdunazarov A., Soliev N. tudy of the performance of frameless construction structures under the influence of vertical stresses of ultra-submerged the lyoss soils //Студенческий вестник. – 2020. – Т. 28. – №. 126 часть 3. – С. 39.
39. Хошимов С. Н. У., Казадаев А. М. УСТАНОВКА ДООЧИСТКИ СТОЧНЫХ ВОД ОТ НЕФТЕПРОДУКТОВ //Вестник Науки и Творчества. – 2017. – №. 3 (15). – С. 147-150.
40. Ювмитов А. С., Казадаев А. М. ИССЛЕДОВАНИЕ РАСПРОСТРАНЕННЫХ ОШИБОК, ДОПУСКАЕМЫХ В ПРОЦЕССЕ СТРОИТЕЛЬСТВА ЗДАНИЙ И СООРУЖЕНИЙ, МЕРЫ ПО ИХ НЕДОПУЩЕНИЮ И УЛУЧШЕНИЮ КАЧЕСТВА СТРОИТЕЛЬСТВА //Central Asian Research Journal for Interdisciplinary Studies (CARJIS). – 2022. – №. Special issue. – С. 140-145.
41. Казадаев А. М., Обидинова Г.Ш., РОЛЬ МАЛОГО БИЗНЕСА И ЧАСТНОГО ПРЕДПРИНИМАТЕЛЬСТВА В РЕСПУБЛИКЕ УЗБЕКИСТАН // Теория и практика современной науки. – 2017. – №. 5 (23). – С. 1005-1008.